

**Mechanical joining - Destructive testing of joints -
Specimen dimensions and test procedure for tensile
shear testing of single joints (ISO 12996:2013)**

EESTI STANDARDI EESSÕNA

NATIONAL FOREWORD

See Eesti standard EVS-EN ISO 12996:2013 sisaldab Euroopa standardi EN ISO 12996:2013 ingliskeelset teksti.	This Estonian standard EVS-EN ISO 12996:2013 consists of the English text of the European standard EN ISO 12996:2013.
Standard on jõustunud sellekohase teate avaldamisega EVS Teatajas.	This standard has been endorsed with a notification published in the official bulletin of the Estonian Centre for Standardisation.
Euroopa standardimisorganisatsioonid on teinud Euroopa standardi rahvuslikele liikmetele kättesaadavaks 03.07.2013.	Date of Availability of the European standard is 03.07.2013.
Standard on kättesaadav Eesti Standardikeskusest.	The standard is available from the Estonian Centre for Standardisation.

Tagasisidet standardi sisu kohta on võimalik edastada, kasutades EVS-i veebilehel asuvat tagasiside vormi või saates e-kirja meiliaadressile standardiosakond@evs.ee.

ICS 25.160.10, 25.160.40

Standardite reprodutseerimise ja levitamise õigus kuulub Eesti Standardikeskusele

Andmete paljundamine, taastekitamine, kopeerimine, salvestamine elektroonsesse süsteemi või edastamine ükskõik millises vormis või millisel teel ilma Eesti Standardikeskuse kirjaliku loata on keelatud.

Kui Teil on küsimusi standardite autorikaitse kohta, võtke palun ühendust Eesti Standardikeskusega:
Aru 10, 10317 Tallinn, Eesti; www.evs.ee; telefon 605 5050; e-post info@evs.ee

The right to reproduce and distribute standards belongs to the Estonian Centre for Standardisation

No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying, without a written permission from the Estonian Centre for Standardisation.

If you have any questions about copyright, please contact Estonian Centre for Standardisation:
Aru 10, 10317 Tallinn, Estonia; www.evs.ee; phone 605 5050; e-mail info@evs.ee

ICS 25.160.40; 25.160.10

English Version

Mechanical joining - Destructive testing of joints - Specimen dimensions and test procedure for tensile shear testing of single joints (ISO 12996:2013)

Assemblage mécanique - Essais destructifs des jonctions - Dimensions des éprouvettes et procédures d'essai pour essais de traction-cisaillement des jonctions uniques (ISO 12996:2013)

Mechanisches Fügen - Zerstörende Prüfung von Verbindungen - Probenmaße und Prüfverfahren für die Scherzugprüfung von Einpunktproben (ISO 12996:2013)

This European Standard was approved by CEN on 15 June 2013.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 12996:2013) has been prepared by Technical Committee ISO/TC 44 "Welding and allied processes" in collaboration with Technical Committee CEN/TC 121 "Welding and allied processes" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2014, and conflicting national standards shall be withdrawn at the latest by January 2014.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 12996:2013 has been approved by CEN as EN ISO 12996:2013 without any modification.

Contents		Page
Foreword		iv
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Test specimens and types of tests	3
5	Test equipment and test procedure	4
6	Failure modes and force-displacement curves	5
7	Test report	5
Annex A (normative) Types of joint failure		7
Bibliography		16

Mechanical joining — Destructive testing of joints — Specimen dimensions and test procedure for tensile shear testing of single joints

1 Scope

This International Standard specifies the geometry of the test specimens and the procedure for the tensile shear testing of single mechanical joints on single and multilayer specimens up to a single sheet thickness of 4,5 mm.

The term sheet, as used in this International Standard, includes extrusions and cast materials.

The purpose of the tensile shear test is to determine the mechanical characteristics and failure modes of the joints made with the different methods.

This International Standard does not apply to civil engineering applications such as metal building and steel construction which are covered by other applicable standards.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2768-1, *General tolerances — Part 1: Tolerances for linear and angular dimensions without individual tolerance indications*

ISO 7500-1, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

3 Terms and definitions

For the purpose of this document, the following terms and definitions apply.

3.1 tensile shear force

F_{\max}
maximum force recorded in the test

Note 1 to entry: If required, further characteristic data, e.g. $F_{p0,2}$ (see 3.2), stiffness of the specimen c (see 3.7) or slope of the force curve, energy dissipation W (see 3.8), can be determined according to the shear diagram given in Figure 4.

3.2 elastic force limit

F_e
force where predetermined plastic or permanent displacement of the test specimen occurs

3.3 slippage force

F_s
force at which a relative movement of the joined parts is registered

3.4 displacement

s
change in the length of a specimen due to the application of a force

[SOURCE: ISO 18592:2009, 1 3.15 modified — symbol changed; “force” replaces “load”]

3.5 displacement at the tensile shear force F_{\max}

$s_{F_{\max}}$
amount of displacement measured at tensile shear force F_{\max}

3.6 displacement at $0,3F_{\max}$

$s_{0,3F_{\max}}$
amount of displacement measured at $0,3F_{\max}$

3.7 stiffness in elastic range

c
ratio of increase of force to the increase of elongation in the elastic range ($c = \Delta F / \Delta s$)

3.8 dissipated energy

W
work or area under the force curve

3.9 dissipated energy up to F_{\max}

$W_{F_{\max}}$
area under the force curve up to the point of maximum tensile shear force F_{\max}

$$W_{F_{\max}} = \int_{s=0}^{s_{F_{\max}}} F \cdot ds$$

3.10 dissipated energy up to $0,3F_{\max}$

$W_{0,3F_{\max}}$
area under the force curve up to the point where the tensile shear force drops to 30 % of F_{\max}

$$W_{0,3F_{\max}} = \int_{s=0}^{s_{0,3F_{\max}}} F \cdot ds$$

Note 1 to entry: The $0,3F_{\max}$ limit was introduced in order to reduce the time for carrying out the tensile shear test, because generally the area under the force curve after $0,3F_{\max}$ does not contribute significantly to the dissipated energy.

3.11 dissipated energy up to fracture

W_{fracture}
total area under the force curve

$$W_{\text{fracture}} = \int_{s=0}^{s_{\text{fracture}}} F \cdot ds$$

3.12
interference fit joint
form fit joint

property of a joint in which the transmission of external forces, in particular shear forces, is effected by geometrical elements which prevent the movement of the components relative to one another

Note 1 to entry: This condition is frequently achieved by the fastener’s outer diameter surface having complete contact with the joint’s component holes.

Note 2 to entry: Compare *clearance fit joint* (3.13).

3.13
clearance fit joint
force fit joint
non-interference fit joint

property of a joint in which external forces, in particular shear forces, are transmitted through friction and if the force to be transmitted is greater than the frictional force, then frictional locking is overcome and the components move relative to one another


Note 1 to entry: This condition is frequently achieved by the fastener’s outer diameter surface having incomplete contact with the joint’s component holes.

Note 2 to entry: Compare *interference fit joint* (3.12).

4 Test specimens and types of tests

See [Figures 1](#) and [2](#).


Tolerances according to ISO 2768-1 are applicable to the dimensions of the specimens given in [Table 1](#).

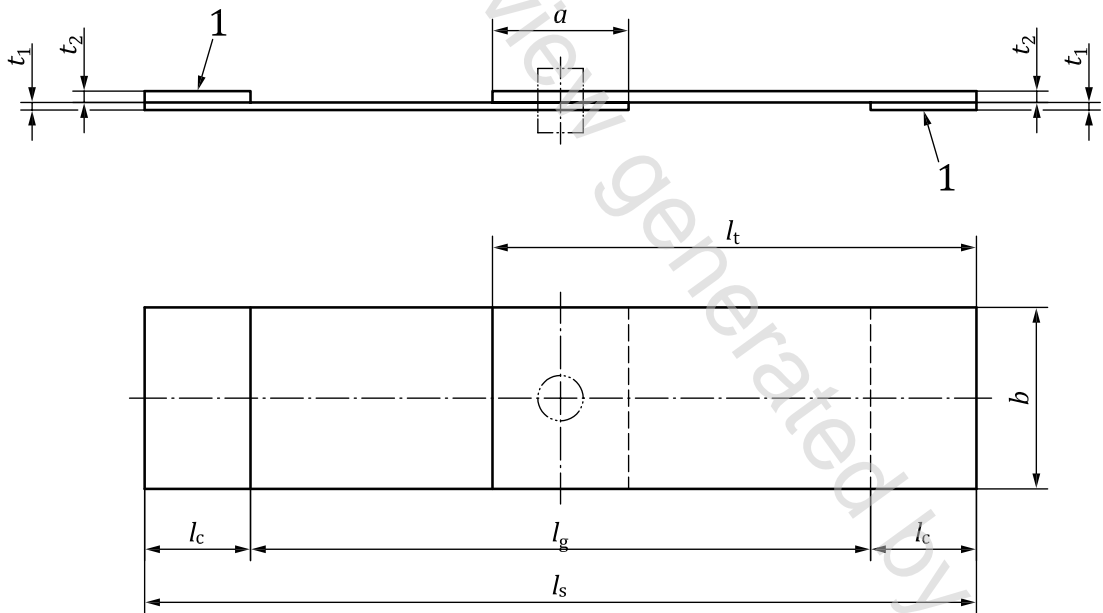

Key

a	overlap	l_s	total length of specimen	t_1, t_2	sheet thickness
b	coupon width	l_g	specimen length between clamps	1	shim plates
l_c	length of clamped area	l_t	coupon length	2	mechanical joint

Figure 1 — Single-lap tensile shear test specimens

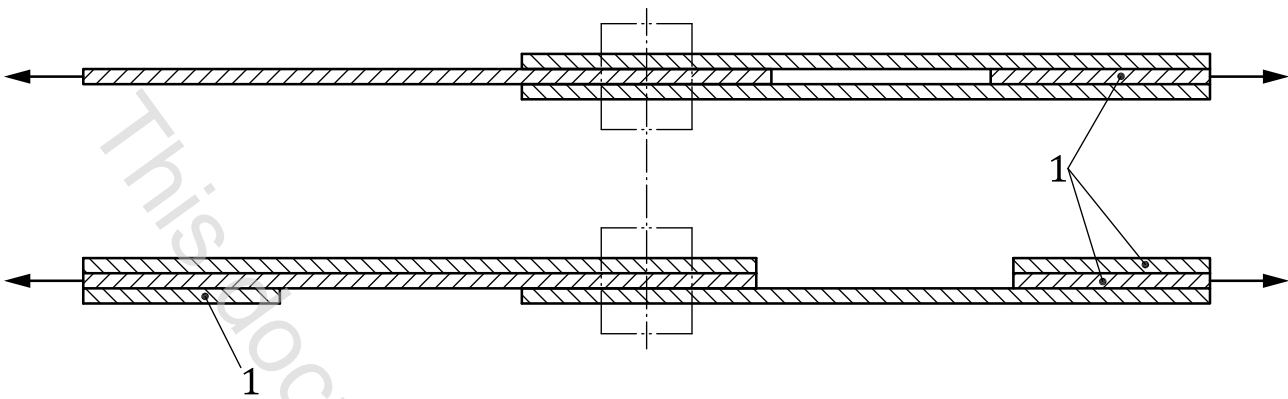

Key
1 shim plates

Figure 2 — Examples of different sheet testing arrangements for tensile shear test specimens

Alternative specimen size, stacking order of the sheets, the joining direction shall be agreed upon between the contracting parties and indicated in the test report.

The appropriate size and tolerance of the hole is determined based on the selected fastener.

Table 1 — Specimen dimensions

Thickness of sheet	Minimum overlap	Minimum speci- men width	Length of clamped area	Specimen length between clamps
t_1, t_2	a	b	l_c	l_g
mm			mm	mm
$\leq 4,5$	$5d$	$7d$	≥ 45	95
NOTE Total specimen length, $l_s = l_g + 2l_c$, where the length of the clamped area is to be selected in accordance with the testing machine being used.				
d Nominal diameter of the fastener or width or diameter of the clinching die.				

5 Test equipment and test procedure

Clamp the test specimen in a tensile testing machine according to ISO 7500-1, in such a manner that the clamps are at the required distance from one another. For sheet thicknesses >1 mm or where the ratio of the thicknesses is >1,4, shim plates shall be used for clamping the test specimen in the grips of the tensile testing machine to ensure force concentricity [see Figure 3 b) and c)]. Shim plates can be joined by suitable joining method, e.g. resistance spot welding, adhesive bonding.

NOTE 1 If identical test results can be achieved by other measures shim plates can be omitted, e.g. by self-aligning clamps.


Testing shall be carried out at room temperature, unless otherwise specified.

The speed of testing is 10 mm/min or less.

NOTE 2 If tests at higher speeds show that the higher testing speed has no influence on the test results, then the higher testing speed may be used for the tensile shear tests.

The displacement shall be measured as the travel of the crosshead or by using extension calliper gauges, laser measuring equipment or other suitable extension sensors with a defined length directly on the specimen. Measurements made using signals from the crosshead shall, if necessary, be corrected by taking the stiffness of the machine into consideration. The sensing method used and the defined length of the specimen measured shall be recorded in the test report.

Tests results are comparable only when the tests are carried out under identical boundary conditions.

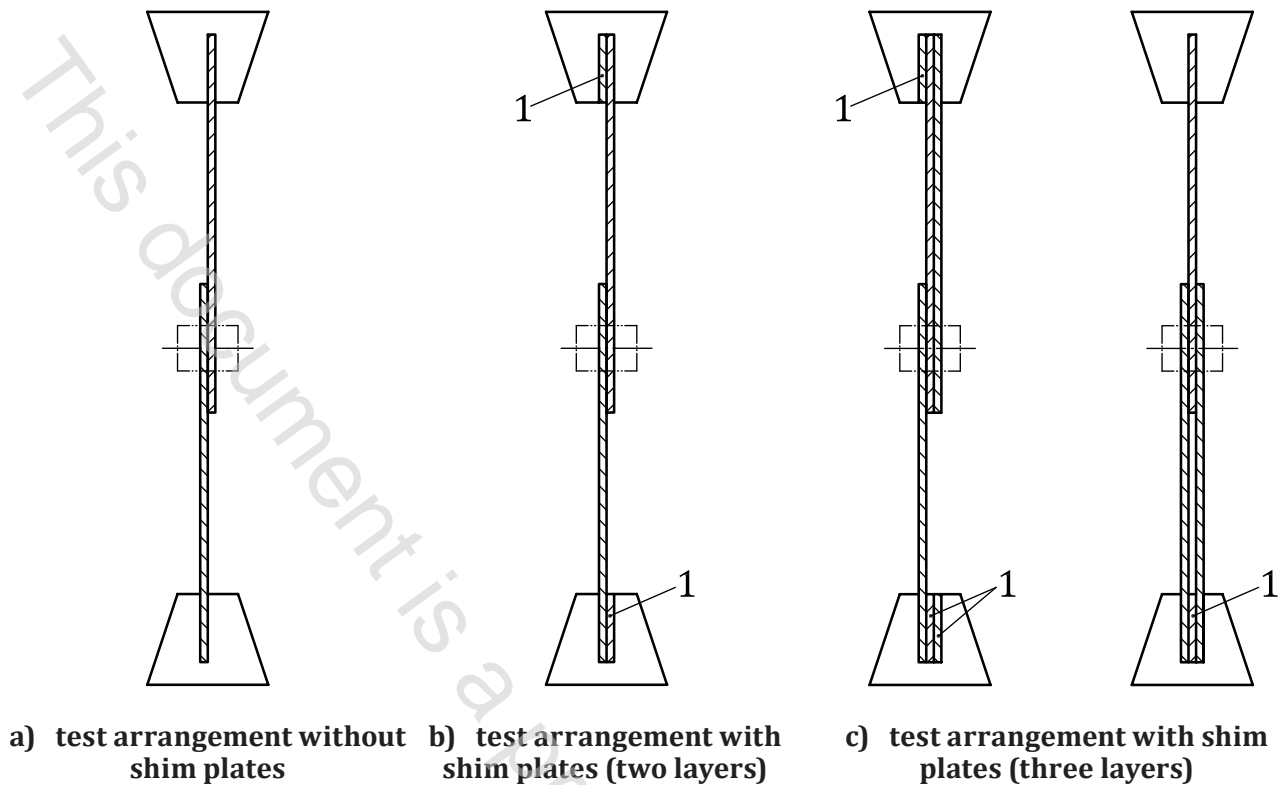

Key

1 shim plates

Figure 3 — Set-up for tensile shear test specimens

[Figure 4](#) illustrates a typical force elongation diagram for specimens with interference and clearance fit joints showing slippage. Different diagrams can be the result of different combinations of joining methods, sheet materials and thicknesses, as well as specimen geometries.

6 Failure modes and force-displacement curves

The failure mode after tensile shear testing shall be classified according to [Annex A](#).

[Figures A.1](#) to [A.8](#) show classification of typical failure modes.


[Figure A.9](#) shows some force-displacement curves.

7 Test report

The test report shall contain the information agreed to between the contracting parties. The content may include some or all items listed below:

- a reference to this International Standard (ISO 12996:2013);
- name of the examiner and/or the examining body;
- date and signature of the examiner and/or the examining body;
- joining technology;

- e) joining parameters and joining equipment, fastener used;
- f) specimen material and material condition;
- g) joining direction, stacking order, location of coated sites;
- h) specimen dimensions;
- i) testing machine, test speed;
- j) defined length on specimen and gauge type used for displacement measurements single values, mean values and standard deviation of the characteristic values;
- k) individual test results, standard deviation, Coefficient of variation for the forces and the displacement;
- l) force–displacement diagrams;
- m) failure mode;
- n) any additional remarks and any deviations from this International Standard.

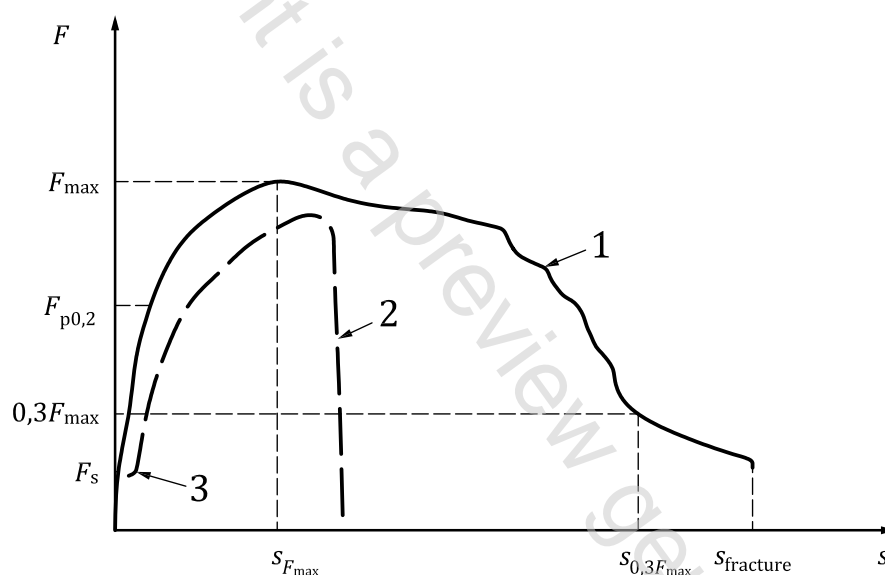

Key

F	force	1	interference fit joint/form fit joint
s	displacement	2	clearance fit joint/force fit joint
		3	slippage

Figure 4 — Characteristic values of a force–displacement diagram for the tensile shear test