
**Non-destructive testing — Magnetic
particle testing —**

**Part 2:
Detection media**

Essais non destructifs — Magnétoscopie —

Partie 2: Produits magnétoscopiques



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

This document is a preview generated by EVS

© ISO 2002

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 9934-2 was prepared by the European Committee for Standardization (CEN) in collaboration with Technical Committee ISO/TC 135, *Non-destructive testing*, Subcommittee SC 2, *Surface methods*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this document, read “...this European Standard...” to mean “...this International Standard...”.

ISO 9934 consists of the following parts, under the general title *Non-destructive testing — Magnetic particle testing*:

- *Part 1: General principles*
- *Part 2: Detection media*
- *Part 3: Equipment*

Contents

	Page
Foreword.....	v
1 Scope	1
2 Normative references	1
3 Terms and definitions.....	1
4 Safety precautions.....	2
5 Classification.....	2
5.1 General.....	2
5.2 Magnetic inks	2
5.3 Powders	2
6 Testing and test certificate	2
6.1 Type testing and batch testing.....	2
6.2 In service testing.....	2
7 Requirements and test methods	2
7.1 Performance	2
7.2 Colour.....	3
7.3 Particle size	3
7.4 Temperature resistance	3
7.5 Fluorescent coefficient and fluorescent stability.....	3
7.6 Fluorescence of carrier liquid.....	5
7.7 Flash point	5
7.8 Corrosion induced by detection media	5
7.9 Viscosity of the carrier liquid.....	5
7.10 Mechanical stability	5
7.11 Foaming	6
7.12 pH	6
7.13 Storage stability	6
7.14 Solids content	6
7.15 Sulphur and halogen content	6
8 Testing requirements	7
9 Test report	7
10 Packaging and labelling.....	7
Annex A (normative) Procedure for type, batch and in service testing	10
Annex B (normative) Reference blocks	12
Annex C (normative) Corrosion testing of steel	17
Bibliography	21

Foreword

This document EN ISO 9934-2:2002 has been prepared by Technical Committee CEN/TC 138 "Non-destructive testing", the secretariat of which is held by AFNOR, in collaboration with Technical Committee ISO/TC 135 "Non-destructive testing".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2003, and conflicting national standards shall be withdrawn at the latest by June 2003.

Annexes A, B and C are normative

This standard consists of the following parts:

EN ISO 9934-1, *Non-destructive testing - Magnetic particle testing - Part 1: General principle (ISO 9934-1:2001)*.

EN ISO 9934-2, *Non-destructive testing - Magnetic particle testing - Part 2: Detection media (ISO 9934-2:2002)*.

EN ISO 9934-3, *Non-destructive testing - Magnetic particle testing - Part 3: Equipment (ISO 9934-3:2002)*.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

This document is a preview generated by EVS

1 Scope

This European Standard specifies the significant properties of magnetic particle testing products (including magnetic ink, powder, carrier liquid, contrast aid paints) and the methods for checking their properties.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text, and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 1330-1, *Non destructive testing - Terminology - Part 1: List of general terms*.

EN 1330-2, *Non destructive testing - Terminology - Part 2: Terms common to the non-destructive testing methods*.

EN 10083-1, *Quenched and tempered steels - Part 1: Technical delivery conditions for special steels*.

EN 10204, *Metallic products - Types of inspection documents*.

EN 12157, *Rotodynamic pumps - Coolant pumps units for machine tools - Nominal flow rate, dimensions*.

EN ISO 2160, *Petroleum products - Corrosiveness to copper - Copper strip test (ISO 2160:1998)*.

EN ISO 3059, *Non-destructive testing - Penetrant testing and magnetic particle testing - Viewing conditions (ISO 3059:2001)*.

EN ISO 3104, *Petroleum products - Transparent and opaque liquids - Determination of kinematic viscosity and calculation of dynamic viscosity (ISO 3104:1994)*.

EN ISO 9934-1, *Non-destructive testing - Magnetic particle testing - Part 1: General principle (ISO 9934-1:2001)*.

EN ISO 9934-3, *Non-destructive testing - Magnetic particle testing - Part 3: Equipment (ISO 9934-3:2002)*.

prEN ISO 12707, *Non-destructive testing - Terminology - Terms used in magnetic particle testing (ISO/DIS 12707:2000)*.

ISO 2591-1, *Test sieving - Part 1: Methods using test sieves of woven wire cloth and perforated metal plate*.

ISO 4316, *Surface active agents - Determination of pH of aqueous solutions - Potentiometric method*.

3 Terms and definitions

For the purposes of this European Standard, the terms and definitions given in EN 1330-1, EN 1330-2 and prEN ISO 12707 together with the following apply.

3.1

batch

quantity of material produced during one manufacturing operation having uniform properties throughout and with a unique identifying number or mark

4 Safety precautions

The materials used in magnetic particle inspection and those used in their testing include chemicals that can be harmful, flammable and/or volatile. All necessary precautions should be observed. All relevant regulations, including national and local regulations pertaining to health and safety, anti-pollution requirements etc., shall be observed.

5 Classification

5.1 General

The magnetic particle materials covered by this specification shall be classified as follows.

5.2 Magnetic inks

Magnetic inks shall consist of finely divided coloured or fluorescent magnetic particles in a suitable carrier liquid. They shall form a uniform suspension when agitated.

Magnetic inks may be produced from products supplied as concentrates, including paste and powders, or ready for use.

5.3 Powders

Powders for the dry technique shall consist of finely divided coloured and/or fluorescent magnetic particles.

6 Testing and test certificate

6.1 Type testing and batch testing

Type testing and batch testing of magnetic particle materials shall be carried out in accordance with the requirements of EN ISO 9934-1, EN ISO 9934-2, and EN ISO 9934-3.

Type testing is carried out in order to demonstrate suitability of a product for the intended use. Batch testing is carried out in order to demonstrate conformity of the characteristics of a batch to the product type specified.

The supplier shall provide a test certificate showing compliance with this standard having used the methods detailed. This certificate shall include results obtained and tolerances allowed.

If any changes are made to the detection media, then a new type test shall be performed.

6.2 In service testing

In service testing is carried out to demonstrate the continued performance of the detection media.

7 Requirements and test methods

7.1 Performance

7.1.1 Type testing and batch testing

Type testing and batch testing shall be carried out according to annex A using the reference blocks types 1 or 2 as described in annex B.

7.1.2 In service testing

In service testing shall be carried out according to annex A using one of the reference blocks types 1 or 2 as described in annex B or a test block which exhibit similar discontinuities to those normally found in components typically processed in the equipment.

7.1.3 Contrast aid paints

Type testing and batch testing shall be carried out according to 7.1.1 after having applied the paint in accordance with the manufacturer instructions and using a type test approved, compatible magnetic ink.

7.2 Colour

The colour of magnetic particles detection media under working conditions shall be stated by the supplier.

The colour of the batch test sample shall not differ from the colour of the type test sample when visually compared.

7.3 Particle size

7.3.1 Method

The method for determination of particle size is dependent on the range of the particle size distribution.

NOTE For magnetic inks the particle-size-distribution can be determined by the Coulter Method or an equivalent method (see Bibliography).

7.3.2 Definition of the particle size

The range of particle size shall be as follows:

- lower diameter d_l : no more than 10 % of the particles shall be smaller than d_l ;
- average diameter d_a : 50 % of the particles shall be larger and 50 % smaller than d_a ;
- upper diameter d_u : no more than 10 % of the particles shall be larger than d_u .

7.3.3 Requirements

d_l , d_a and d_u shall be reported. For magnetic inks sizes shall lie in the range $d_l \geq 1,5 \mu\text{m}$ and $d_u \leq 40 \mu\text{m}$.

NOTE For powders d_l is generally $\geq 40 \mu\text{m}$.

7.4 Temperature resistance

There shall be no degradation of the product after 5 minutes heating at the maximum temperature specified by the supplier. This shall be verified by repeating the performance test as specified in 7.1.1.

7.5 Fluorescent coefficient and fluorescent stability

To carry out these tests it is necessary to use dry powder. For magnetic inks the magnetic particle solid content shall be used.

7.5.1 Type testing

7.5.1.1 Method

The fluorescent coefficient β in cd/W is defined as follows:


$$\beta = L/E_e$$

where L = luminance in cd/m^2 of a plane powder surface;

E_e = level of UV-irradiance in W/m^2 at the surface of the powder.

The arrangement of the apparatus used is shown in Figure 1.

The powder surface shall be evenly irradiated with UV(A) at an angle of $45^\circ (\pm 5^\circ)$. Luminance shall be measured with a suitable meter with an accuracy of $\pm 10\%$. It shall measure the luminance from the powder surface and be unaffected by areas outside of the target area. The level of irradiance shall be measured with a meter conforming to EN ISO 3059 with its UV sensor replacing the powder surface.

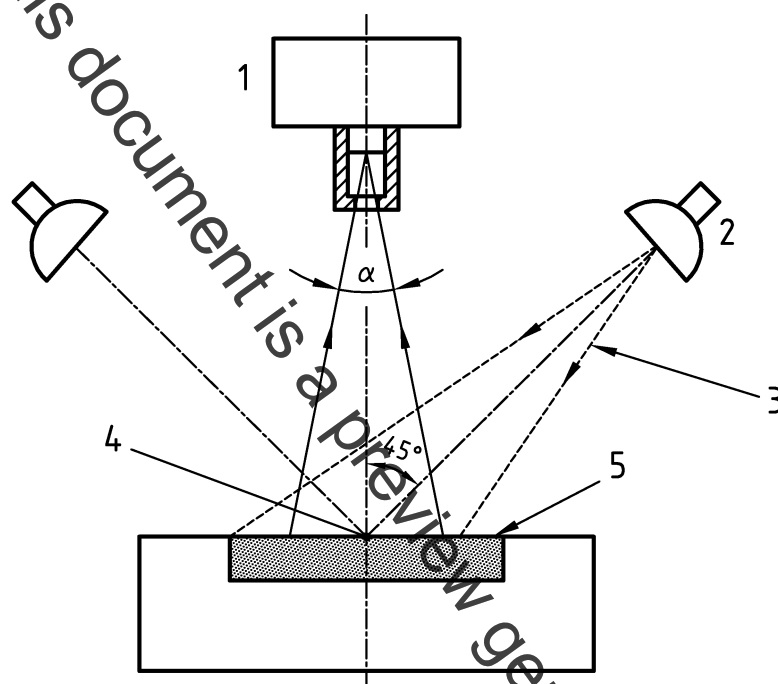

Key

- 1 Measurement of luminance
- 2 Lamp
- 3 UV radiation
- 4 Measurement point of the irradiance
- 5 Powder surface

Figure 1 - Determination of the fluorescent coefficient β for magnetic particles

NOTE A recommended arrangement is using a luminance meter with a 200 cd/m^2 range and a viewing angle (α) of 20° placed 80 mm above the plane powder surface, diameter 40 mm. UV (A) lamps are placed so as to give an even irradiance at the powder surface, with E_e between 10 W/m^2 and 15 W/m^2 .

7.5.1.2 Requirements

The fluorescent coefficient (β) shall be greater than $1,5 \text{ cd/W}$.

7.5.1.3 Fluorescence stability

The sample shall first be tested according to the method described in 7.5.1.1.

The sample shall then be exposed and re-tested as described in 7.5.1.1 after 30 minutes of exposure to UV-A irradiance of 20 W/m² (minimum). The fluorescent coefficient shall not decrease more than 5 %.

7.5.2 Batch testing

Batch testing shall be carried out according to 7.5.1.1. The fluorescent coefficient shall be within 10 % of the type test value.

7.6 Fluorescence of carrier liquid

The fluorescence of the carrier liquid shall be checked by visually comparing with quinine sulphate solution when irradiated with UV-A of at least 10 W/m².

The concentration of the quinine sulphate solution shall be 7×10^{-9} M (5,5 ppm) in 0,1 N H₂SO₄.

The carrier liquid under test shall exhibit no more fluorescence than the quinine sulphate solution.

7.7 Flash point

For magnetic inks, other than water based, the flash point (open cup method) of the carrier fluid shall be reported.

7.8 Corrosion induced by detection media

7.8.1 Corrosion testing on steel

The corrosive effect on steel shall be tested and reported according to annex C.

7.8.2 Corrosion testing of copper

The corrosive effect on copper shall be tested according to EN ISO 2160.

7.9 Viscosity of the carrier liquid

The viscosity shall be tested according to EN ISO 3104.

The dynamic viscosity shall not be higher than 5 mPa·s at 20 °C (± 2 °C).

7.10 Mechanical stability

7.10.1 Long term test (endurance test)

The manufacturer shall show that the detection media is unaffected by use in a typical magnetic particle testing bench over a period of 120 h.

This may be proven in a magnetic particle testing bench or by using an arrangement to simulate this; a recommended arrangement is as follows:

a 40 l sample of the detection media shall be contained in a corrosion resistant reservoir fitted with a centrifugal pump. The detection media shall be recirculated and the flow interrupted by a valve.

Technical data:

Type of the sump pump EN 12157 - T 160-270-1

Diameter of the return flow RI 1" NB pipe

Cycle time

— valve opened 5 s

— valve closed 5 s

The detection media shall be checked with a reference block (see 7.1.1) before use and after 120 h.

Any discernible change in the quality of indications shall be cause for rejection.

7.10.2 Short term test

7.10.2.1 Equipment

A stirring arrangement similar to Figure 2 shall be used.

- 1) Speed of stirring blade: $(3\,000 \pm 300)$ rpm.
- 2) Stirring cup: Capacity 2 l.
- 3) Reference blocks type 1 and type 2 as detailed in annex B.
- 4) UV-A source to give irradiance of 10 W/m^2 , to the requirement of EN ISO 3059.

7.10.2.2 Procedure

Stir a 1 l sample for 2 h. Compare the indications on reference block N° 1 and N° 2 produced by the stirred probe and the reference probe.

7.10.2.3 Requirements

Any discernible change in the quality of indications shall be cause for rejection.

7.11 Foaming

Foaming shall be checked during mechanical stability test to 7.10.1 or 7.10.2. Significant foaming shall be cause for rejection.

7.12 pH

The pH of aqueous carrier liquids shall be determined according to ISO 4316. The value shall be reported.

7.13 Storage stability

The expiry date shall be given by the producer and shall be marked on each original container.

7.14 Solids content

The recommended magnetic particle content in g/l of magnetic inks shall be given by the supplier.

7.15 Sulphur and halogen content

For products designated low in sulphur and halogens, the sulphur and halogen content shall be determined by a suitable method which is accurate to ± 10 ppm at 200 ppm of sulphur/halogens.

— Sulphur content shall be less than 200 ppm (± 10);

— Halogens content shall be less than 200 ppm (± 10), (halogens shall be taken as chlorine + fluorine).

8 Testing requirements

Testing shall be carried out according to the requirements of Table 1.

Type testing (Q) and batch testing (B) shall be the responsibility of the supplier or manufacturer. In service testing (P) shall be the responsibility of the user.

9 Test report

As agreed at the time of the order, the manufacturer or the supplier of the magnetic particle testing materials shall provide a certificate of compliance according to EN 10204.

Results of all tests required in Table 1 shall be reported.

10 Packaging and labelling


Packaging and labelling shall be in accordance with all applicable national and local regulations. Containers shall be compatible with the detection media. Containers shall be marked with the following information:

- product identification;
- type of detection media;
- batch number;
- date of manufacture;
- expiry date.

Table 1 - Testing requirements

Properties	Contrast aid paints	Dry detection media	Organic carrier liquid	Aqueous suspension ready for use	Organic suspension ready for use	Method	
						Clause	Standard/Remarks
Performance	Q/B	Q/B/P		Q/B/P	Q/B/P	7.1	by comparison
Colour	Q/B/P	Q/B/P	Q	Q/B/P	Q/B/P	7.2	
Particle size		Q/B		Q/B	Q/B	7.3	
Temperature resistance		Q	Q	Q	Q	7.4	
Fluorescence coefficient		Q/B		Q/B	Q/B	7.5	
Fluorescence stability		Q		Q	Q	7.5.1.3	by comparison
Flash point	Q/B		Q/B		Q/B	7.7	
Fluorescence of carrier liquid		Q/B	Q/B	Q/B		7.6	
Corrosion on steel	Q			Q		7.8.1	
Corrosion on copper				Q	Q	7.8.2	EN ISO 2160
Viscosity			Q	Q/B	Q/B	7.9	EN ISO 3104
Mechanical stability: short test				Q/B	Q/B	7.10	ISO 4316
long term test				Q	Q	7.10	
Foaming			Q	Q/B	Q/B	7.11	
pH (aqueous products)				Q		7.12	
Storage stability	Q	Q/B	Q/B	Q/B	Q/B	7.13	
Sulphur & Halogen content	B		B	B	B	7.15	NOTE Only for products designated low in sulphur/halogen
NOTE Q : type testing B : batch testing P : in service testing							

Dimensions in millimetres

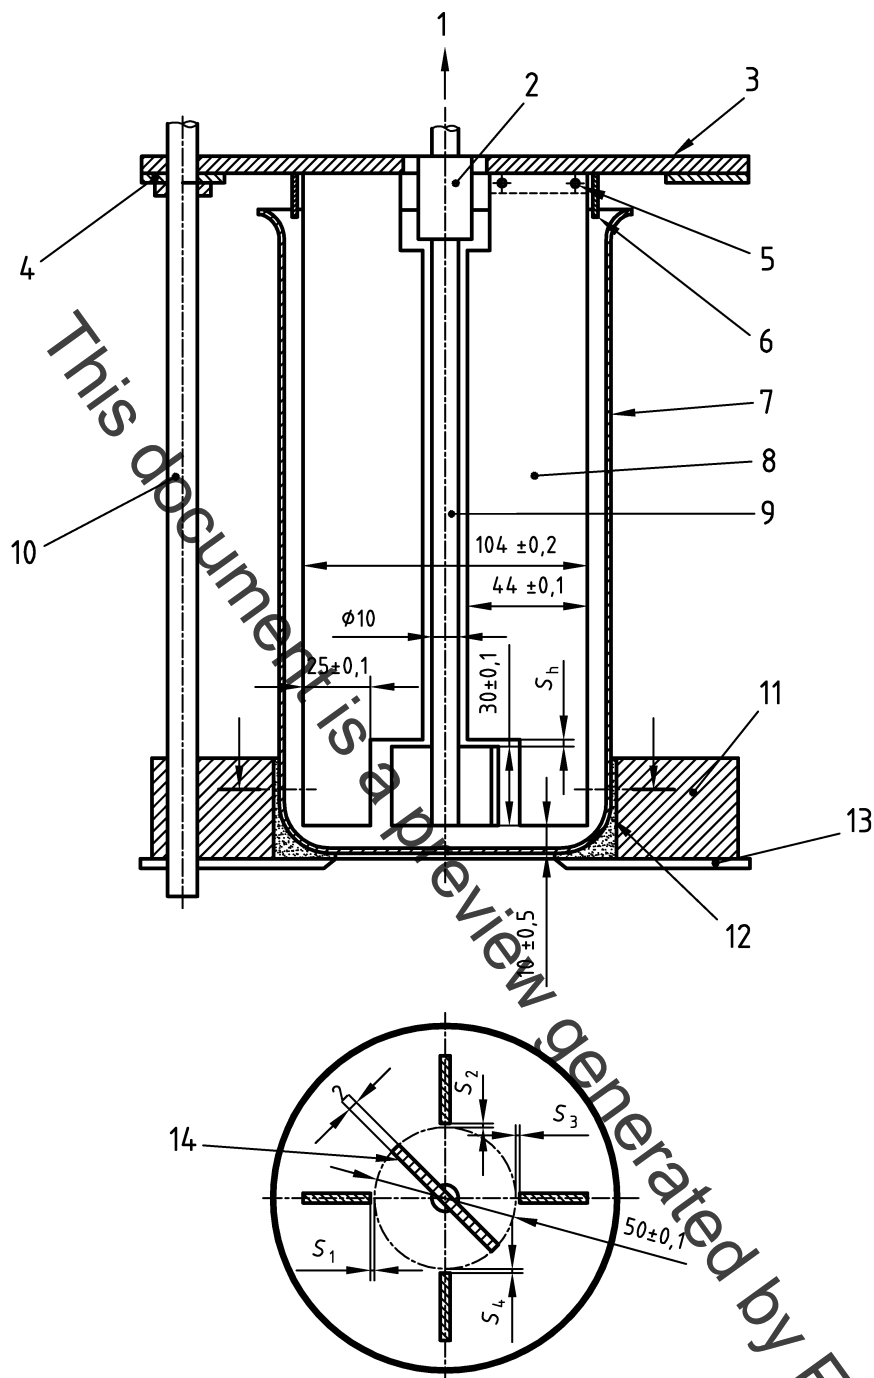

Material: non
ferromagnetic
steel protected
against
corrosion

Gap dimensions

$$s_h = 2 \pm 0,5$$

$$s_1, \dots, s_4 = 2 \pm 0,5 (s_1 + s_3) / 2 = 2 \pm 0,2 (s_2 + s_4) / 2 = 2 \pm 0,2$$

Tolerances are to be
ensured in the 4 blade
positions

Key

- 1 Motor
- 2 Clutch
- 3 Motor plate
- 4 Support ring distance setting 10 mm from the bottom
- 5 Fixture by angle profiles
- 6 Spraying plate
- 7 Cup ISO 3819 - HF 2000
- 8 4 stator plates, 2 mm thick - Height of support ~ 170 mm

- 9 Axle
- 10 3 supports
- 11 Pilot ring
- 12 Felt
- 13 Basic plate
- 14 Blade

Figure 2 - Construction of the stirring arrangement to 7.10.2

Annex A (normative)

Procedure for type, batch and in service testing

A.1 Preparation of the detection media

The detection media shall be prepared in accordance with the manufacturer's instructions.

A.2 Cleaning of the reference blocks

The reference block shall be cleaned by a suitable method to ensure that it is free from fluorescent material, oxide, dirt and grease and has a water break free surface.

A.3 Application of the detection media

Detection media shall be applied to reference blocks No. 1 and No. 2 as detailed in annex B in accordance with EN ISO 9934-1.

Spraying: 3 s to 5 s.

Specimen pitch angle: $45^\circ \pm 10^\circ$.

Spraying direction: $90^\circ \pm 10^\circ$ to the surface under examination.

A.4 Inspection and interpretation

A.4.1 Inspection

Test pieces shall be inspected under viewing conditions described in EN ISO 2059.

A.4.2 Interpretation

A.4.2.1 Type and batch testing

The test shall be carried out three times and an average of the results shall be used. Indications shall be evaluated visually or by an equivalent measuring method.

A.4.2.1.1 Reference block type 1

The indications shall be compared to those produced by the reference detection media (e.g. by a photograph).

The result shall be reported.

A.4.2.1.2 Reference block type 2

The cumulative length of the indications shall be reported.

A.4.2.2 In service testing

Using test block type 1 or type 2 the indications produced shall be compared with known results.

A.5 Contrast aid paint

Contrast aid paint shall be tested in accordance with A.1 to A.4.2.1, except that the contrast aid paint shall be applied in accordance with the manufacturer's instructions after cleaning the reference test block (see A.2).

This document is a preview generated by EVS