
**Plastics — Epoxy resins — Determination
of chlorine content —**

**Part 3
Total chlorine**

*Plastiques — Résines époxydes — Détermination de la teneur en
chlore*

Partie 3: Chlore total



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

This document is a preview generated by EVS



COPYRIGHT PROTECTED DOCUMENT

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction.....	v
1 Scope.....	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Reagents	2
6 Apparatus	3
7 Procedure	3
8 Expression of results	4
9 Precision	4
10 Test report.....	5
Bibliography.....	6

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 21627-3 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 12, *Thermosetting materials*.

This second edition cancels and replaces the first edition (ISO 21627-3:2002), which has been technically revised.

ISO 21627 consists of the following parts, under the general title *Plastics — Epoxy resins — Determination of chlorine content*:

- *Part 1: Inorganic chlorine*
- *Part 2: Easily saponifiable chlorine*
- *Part 3: Total chlorine*

Introduction

In producing epoxy resins based on epichlorohydrin, impurities containing chlorine may be formed. These are shown below. Since these impurities could impair the final properties of the cured resins, it is necessary to control their formation. Their chemical activities differ significantly, so different analytical procedures are needed for their analysis.


ISO 21627 specifies methods for the determination of these organic and inorganic chlorides which occur as impurities in epoxy resins derived from epichlorohydrin:

- Part 1: Inorganic chlorine (also called ionic chlorine).
- Part 2: Easily saponifiable chlorine, consisting mainly of chlorine which is present as 1,2-chlorohydrin as the result of incomplete dehydrohalogenation.
- Part 3: Total chlorine, consisting mainly of all saponifiable organic chlorine, e.g. 1,2-chlorohydrin, 1,3-chlorohydrin and 1-chloro-2-glycidylether (chloromethyl derivative) which are the result of incomplete dehydrohalogenation, along with inorganic chlorine present in the test portion of epoxy resin.

Since the purposes of Parts 1 to 3 of ISO 21627 differ, one of these methods should be selected, depending on the impurities to be measured.

For analytical methods for impurities other than those shown below, see ISO 4615.

Typical types of inorganic and organic chlorine impurity are shown below:

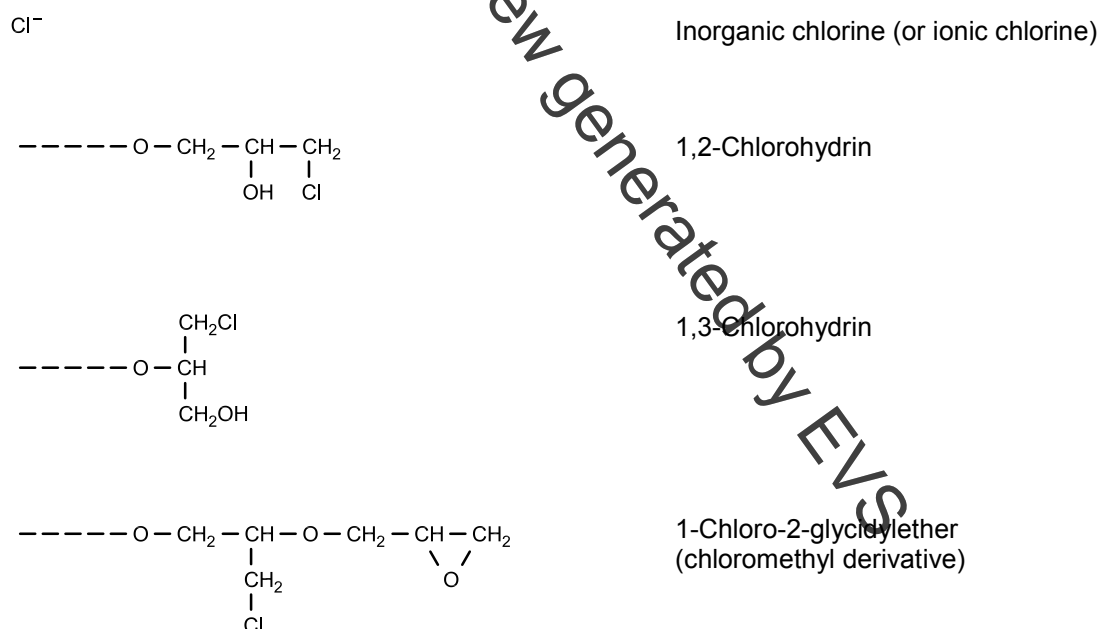

This document is a preview generated by EVS

Plastics — Epoxy resins — Determination of chlorine content —

Part 3: Total chlorine

SAFETY STATEMENT — Persons using this document should be familiar with normal laboratory practice, if applicable. This document does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any regulatory requirements.

1 Scope

This part of ISO 21627 specifies a method for the determination of the total amount of chlorine in epoxy resins.

The chlorine measured by this method, referred to as total chlorine, includes saponifiable organic chlorine and inorganic chlorine.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3696:1987, *Water for analytical laboratory use — Specification and test methods*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

total chlorine

amount of chlorine measurable by this method

NOTE It consists mainly of all saponifiable organic chlorine, e.g. 1,2-chlorohydrin, 1,3-chlorohydrin and 1-chloro-2-glycidylether which are the result of incomplete dehydrohalogenation, along with inorganic chlorine present in the test portion of epoxy resin.

4 Principle

A test portion is dissolved in diethylene glycol monobutyl ether and the solution saponified with an alcoholic solution of potassium hydroxide by heating under reflux. The total chlorine content is then determined by potentiometric titration of the solution with silver nitrate solution.